

## GRAVILLON 10/14 mm NF



**Péetrographie :** CALCAIRE DUR VISEEN  
**Elaboration :** TERTIAIRE

### Partie contractuelle

Valeurs spécifiées sur lesquelles le producteur s'engage

Classe granulaire

Norme

Code

10 14

Norme NF P 18-545 Article 7

C III (01/01/2012)


	0.063	0.5	d/2 5	6.3	8	d 10	12.5	D 14	16	20	1.4D 28	2D 28	EN_FI
Etendue e	2		5			10		10		2	0		
Incertitude U	0.3		1			5		5		1	0		4
V.S.S.+U	2.3		6			18		95		100	100		24.00
V.S.S.	2.0		5			13		90		100	100		20.00
V.S.I.	0.0		0			3		80		98	100		
V.S.I.-U	0.0		0			0		75		97	100		
Ecart-type max	0.61		1.52			3.03		3.03		0.61	0.00		

### Partie informative

Résultats de production

du 02/01/18 au 27/06/18

	0.063	0.5	5	6.3	8	10	12.5	14	16	20	28	EN_FI
Maximum	1.9	3	5	6	9	13	66	90	100	100	100	17.00
Xf+1.25xEcart-types	1.5	2	3	4	5	10	62	89	100	100	100	
Moyenne Xf	1.1	1	2	3	3	7	52	86	99	100	100	12.00
Xf-1.25xEcart-types	0.7	1	1	1	1	4	41	82	98	100	100	
Minimum	0.6	1	1	1	1	3	35	80	96	100	100	9.00
Ecart-type	0.29	0.4	1.0	1.2	1.5	2.4	8.3	2.8	1.0	0.0	0.0	2.777
Nombre de résultats	56	56	56	56	56	56	56	56	56	56	56	7

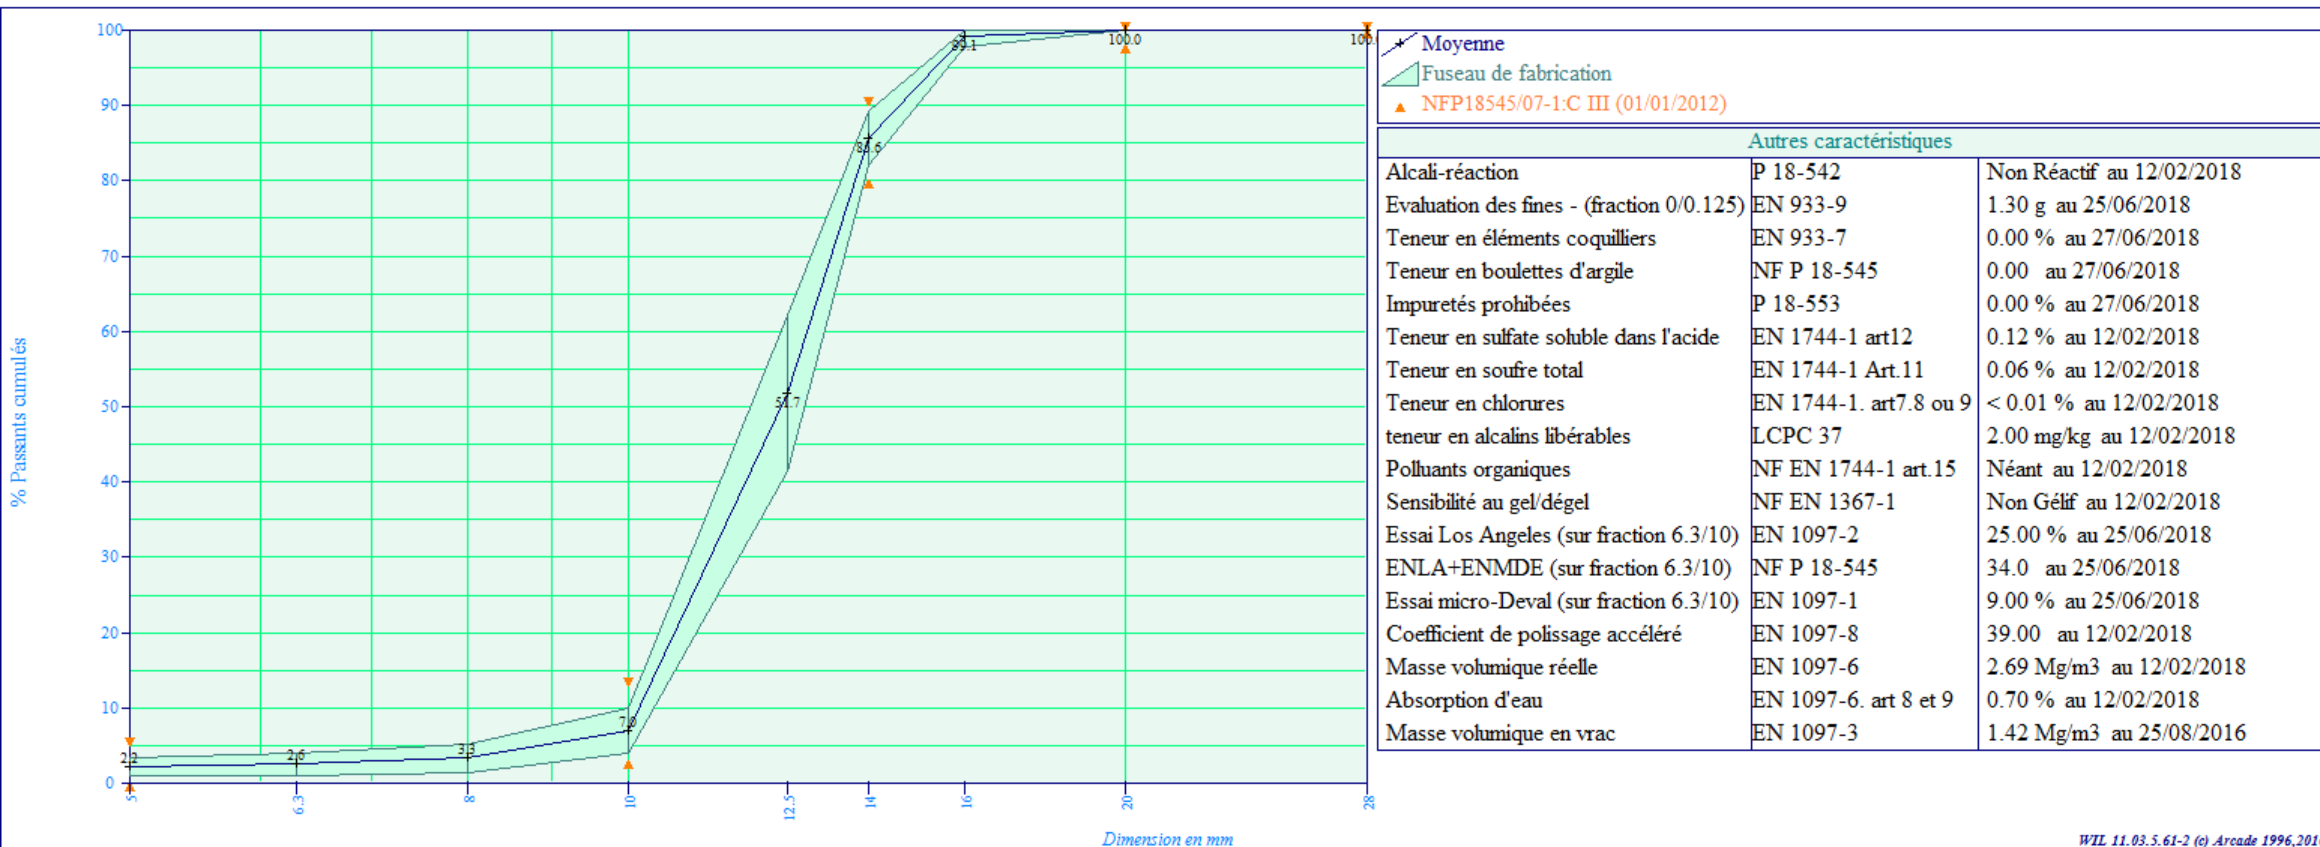

le Responsable Laboratoire

E. COLIN