

## GRAVILLON 20/31.5 mm



**Pétrographie :** CALCAIRE DUR VISEEN  
**Elaboration :** TERTIAIRE

### Partie contractuelle

Valeurs spécifiées sur lesquelles le producteur s'engage

Classe granulaire

Norme

Code

20 31.5

Norme NF P 18-545 Article 7

C III (01/07/2012)


	0.063	0.5	d/2 10	12.5	14	16	d 20	D/1.4 22.4	25	28	D 31.5	40	1.4D 45	2D 63	FI
Etendue e	2		5				10				10		2	0	
Incertitude U	0.3		1				5				5		1	0	4
V.S.S.+U	2.3		6				17				99		100	100	24.00
V.S.S.	2.0		5				12				94		100	100	20.00
V.S.I.	0.0		0				2				84		98	100	
V.S.I.-U	0.0		0				0				79		97	100	
Ecart-type max	0.61		1.52				3.03				3.03		0.61	0.00	

### Partie informative

Résultats de production

du 08/01/18 au 27/06/18

	0.063	0.5	10	12.5	14	16	20	22.4	25	28	31.5	40	45	63	FI
Maximum	1.4	2	3	3	4	4	9	24	51	80	94	100	100	100	12.00
Xf+1.25xEcart-types	1.0	1	2	2	2	2	6	20	45	72	92	100	100	100	
Moyenne Xf	0.7	1	1	1	1	1	4	13	35	63	88	100	100	100	8.43
Xf-1.25xEcart-types	0.4	1	0	1	1	1	2	7	26	54	85	100	100	100	
Minimum	0.3	0	0	0	0	1	2	2	23	50	85	99	100	100	3.00
Ecart-type	0.23	0.3	0.5	0.5	0.6	0.7	1.7	5.3	7.6	7.4	2.7	0.2	0.0	0.0	2.821
Nombre de résultats	46	46	46	46	46	46	46	46	46	46	46	46	46	46	7

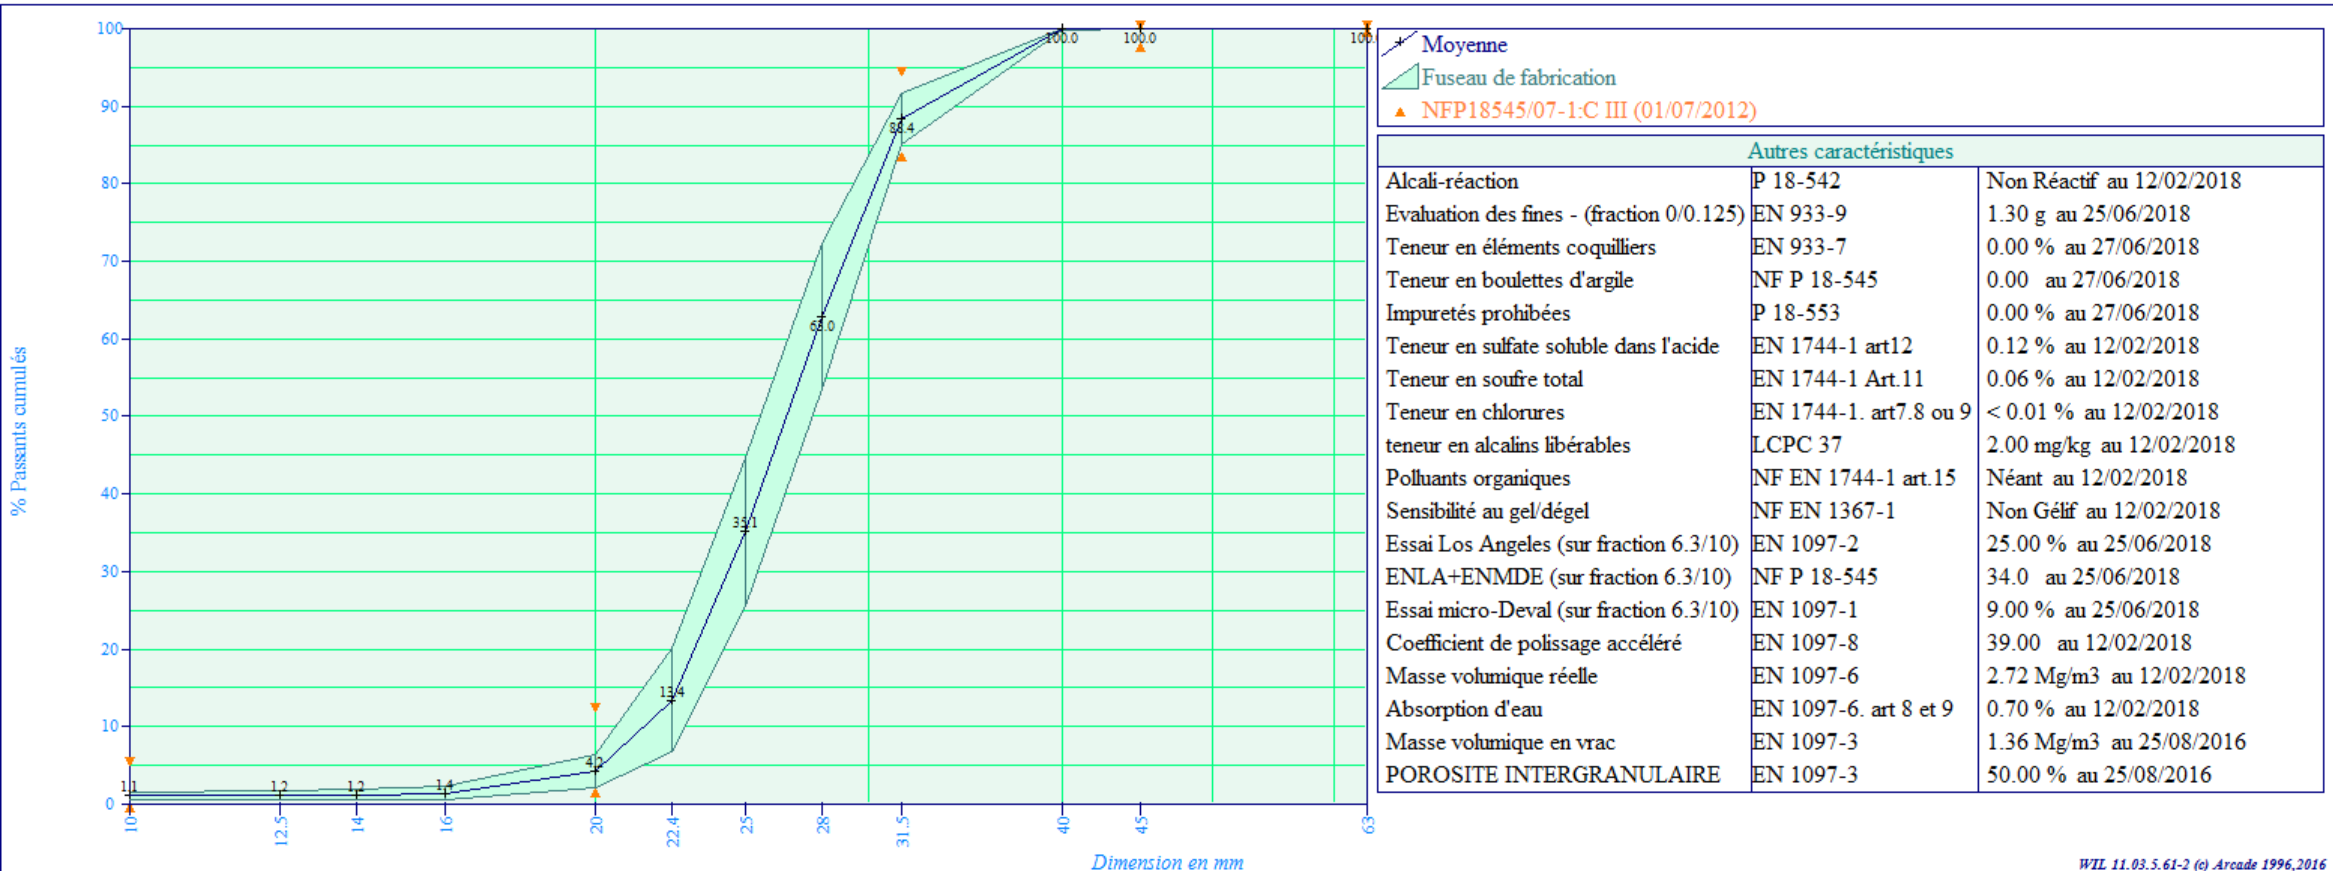

le Responsable Laboratoire

E. COLIN