

10/31.5 (Recomposé)



Partie contractuelle

Valeurs spécifiées sur lesquelles le producteur s'engage

Classe granulaire

10 31.5

Norme

Norme NF P 18-545 Article 7

Code


C III (01/01/2012)

	d/2		d										D/1.4		D		1.4D		2D		FI
	0.063	0.5	5	6.3	8	10	12.5	14	16	18	20	22.4	25	28	31.5	40	45	63			
Etendue e	2		5			10						30			9		2	0			
Incertitude U	0.6		1			5						6			5		1	0	4		
V.S.S.+U	2.6		6			16						76			100		100	100	24.00		
V.S.S.	2.0		5			11						70			99		100	100	20.00		
V.S.I.			0			1						40			90		98	100			
V.S.I.-U			0			0						34			85		97	100			
Ecart-type max	0.61		1.52			3.03						9.09			2.73		0.61	0.00			

Produit recomposé Résultats de production

du 11/10/18 au 10/12/18

	0.063	0.5	5	6.3	8	10	12.5	14	16	18	20	22.4	25	28	31.5	40	45	63	FI
Maximum	1.4	2	3	3	4	6	24	31	41	47	53	63	76	87	97	100	100	100	11.00
Xf+1.25xEcart-types	1.3	2	3	3	3	5	22	31	41	46	51	60	73	86	96	100	100	100	
Moyenne Xf	1.0	1	2	2	2	4	17	29	38	44	49	56	68	81	94	100	100	100	9.48
Xf-1.25xEcart-types	0.6	1	1	1	1	2	13	27	36	42	47	52	62	77	92	100	100	100	
Minimum	0.5	1	1	1	1	2	11	25	35	41	47	50	61	73	92	100	100	100	7.71
Ecart-type	0.27	0.4	0.7	0.7	0.8	1.2	3.6	1.6	1.7	1.5	1.6	3.2	4.5	3.8	1.4	0.0	0.0	0.0	1.357
Nombre de résultats	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	45	6

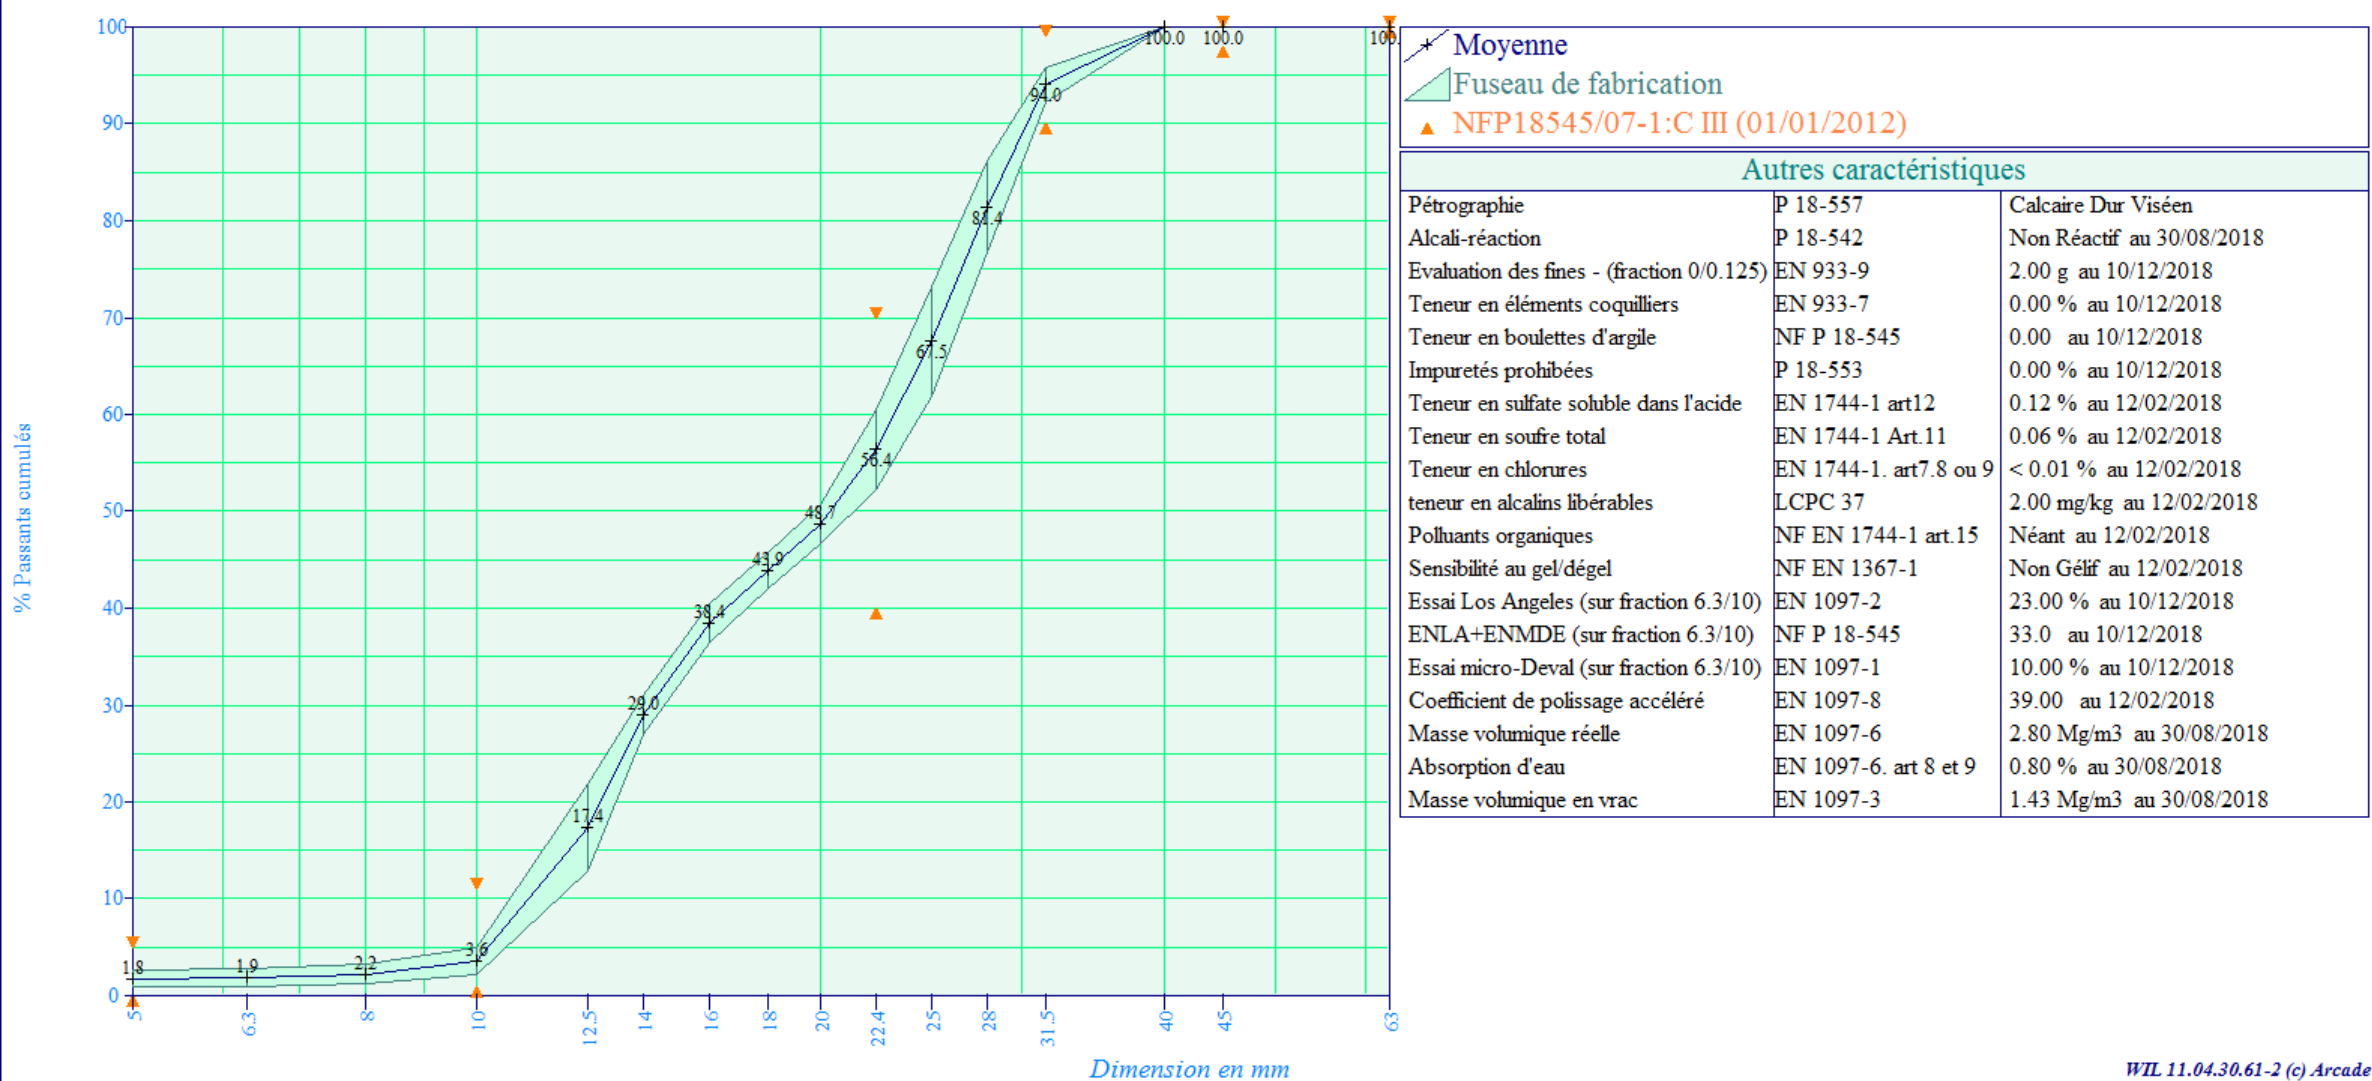

le Responsable Laboratoire

E. COLIN