

# CARBO 0/14


**Péetrographie : CALCAIRE DUR VISEEN**

SCALPAGE TRAITE A 1% DE CHAUX CL90-Q (R5,P2)

### Résultats de production

du 11/07/18 au 12/12/18

	0.063	0.08	0.125	0.25	0.5	1	2	4	5	6.3	8	10	12.5	14	16	20	28	31.5	MB	VBS	
Maximum	12.71	13.26	16.28	20.98	26.03	32.06	42.04	58.24	65.09	74.96	85.70	94.69	99.81	100.00	100.00	100.00	100.00	100.00	100.00	2.90	0.12
Xf+1.25xEcart-types	11.60	12.24	14.60	19.49	24.48	30.85	41.19	57.76	65.24	74.71	85.70	94.94	99.64	100.00	100.00	100.00	100.00	100.00	100.00	2.70	0.09
Moyenne Xf	9.80	10.23	11.97	15.94	21.05	26.97	36.61	51.53	58.56	67.82	78.86	91.55	98.74	99.58	99.95	100.00	100.00	100.00	100.00	1.85	0.06
Xf-1.25xEcart-types	8.00	8.21	9.34	12.38	17.61	23.08	32.04	45.29	51.87	60.94	72.01	88.16	97.84	99.07	99.78	100.00	100.00	100.00	100.00	1.01	0.03
Minimum	7.42	7.59	8.61	12.30	17.79	23.23	32.11	44.49	50.14	59.42	68.69	85.85	96.87	98.89	99.60	100.00	100.00	100.00	100.00	1.00	0.04
Ecart-type	1.439	1.613	2.104	2.841	2.749	3.110	3.663	4.987	5.351	5.508	5.474	2.712	0.717	0.405	0.137	0.000	0.000	0.000	0.000	0.677	0.024
Nombre de résultats	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15	15

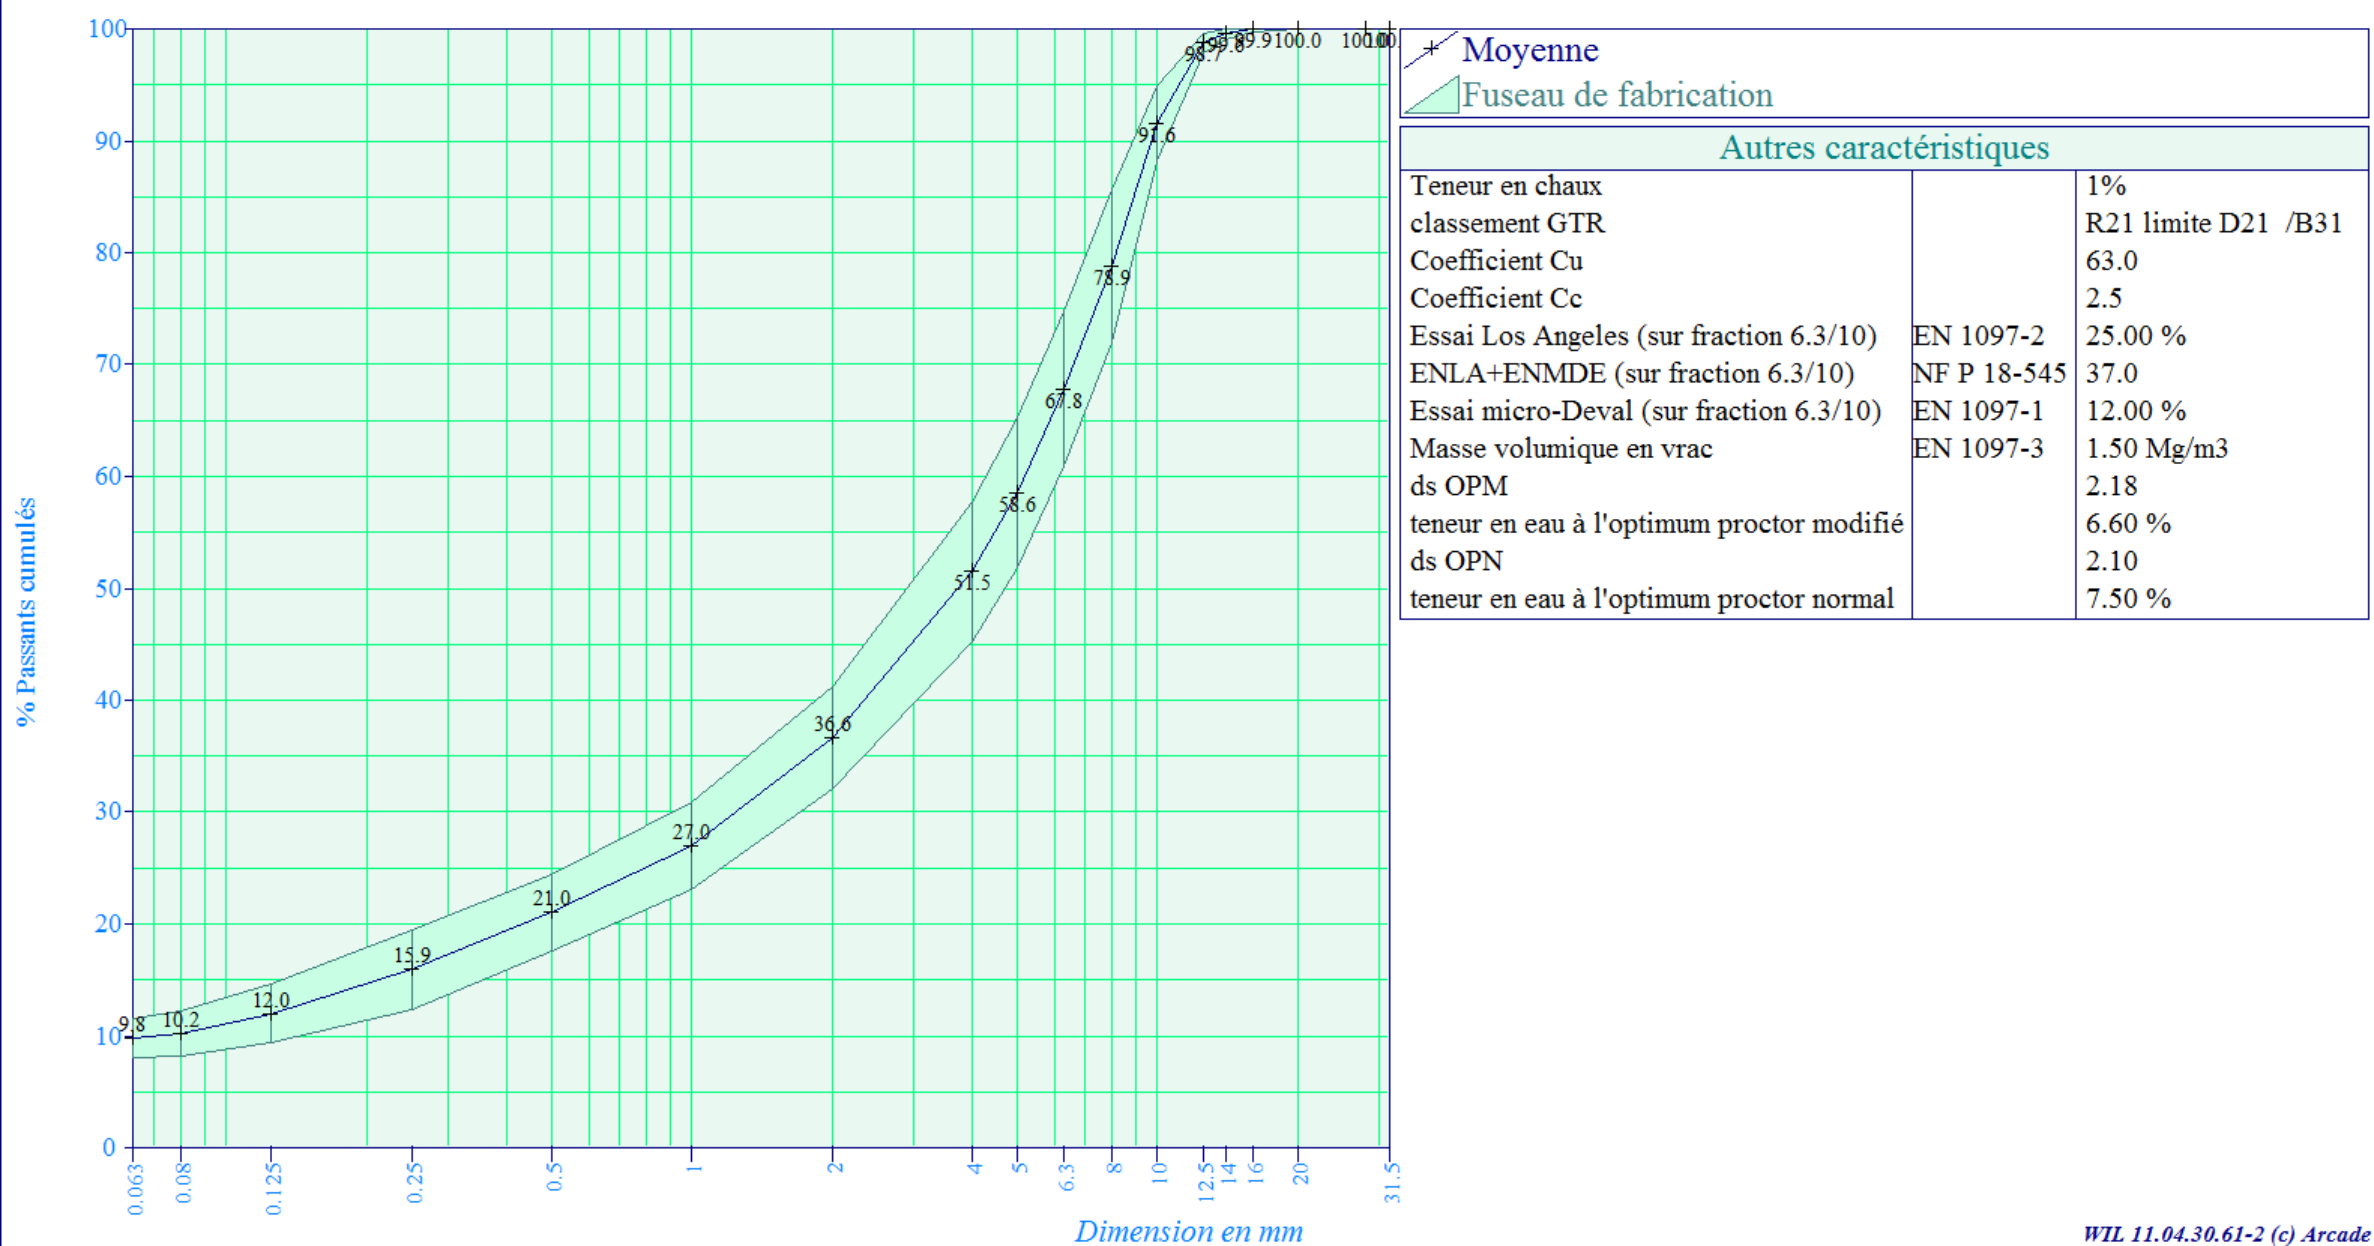

le Responsable Laboratoire

E. COLIN